

Tunable fishnet metamaterials infiltrated by liquid crystals

Alexander Minovich, Dragomir N. Neshev, David A. Powell, Ilya V. Shadrivov, and Yuri S. Kivshar

Citation: *Applied Physics Letters* **96**, 193103 (2010); doi: 10.1063/1.3427429

View online: <http://dx.doi.org/10.1063/1.3427429>

View Table of Contents: <http://scitation.aip.org/content/aip/journal/apl/96/19?ver=pdfcov>

Published by the AIP Publishing

Articles you may be interested in

[Voltage tunable short wire-pair type of metamaterial infiltrated by nematic liquid crystal](#)

Appl. Phys. Lett. **97**, 134103 (2010); 10.1063/1.3496034

[Tunable magnetic response of metamaterials](#)

Appl. Phys. Lett. **95**, 033115 (2009); 10.1063/1.3182857

[Tunability of wire-grid metamaterial immersed into nematic liquid crystal](#)


J. Appl. Phys. **103**, 036101 (2008); 10.1063/1.2837099

[Electrically tunable negative permeability metamaterials based on nematic liquid crystals](#)

Appl. Phys. Lett. **90**, 011112 (2007); 10.1063/1.2430485

[Tunable photonic band schemes of opals and inverse opals infiltrated with liquid crystals](#)

J. Appl. Phys. **92**, 5658 (2002); 10.1063/1.1516868

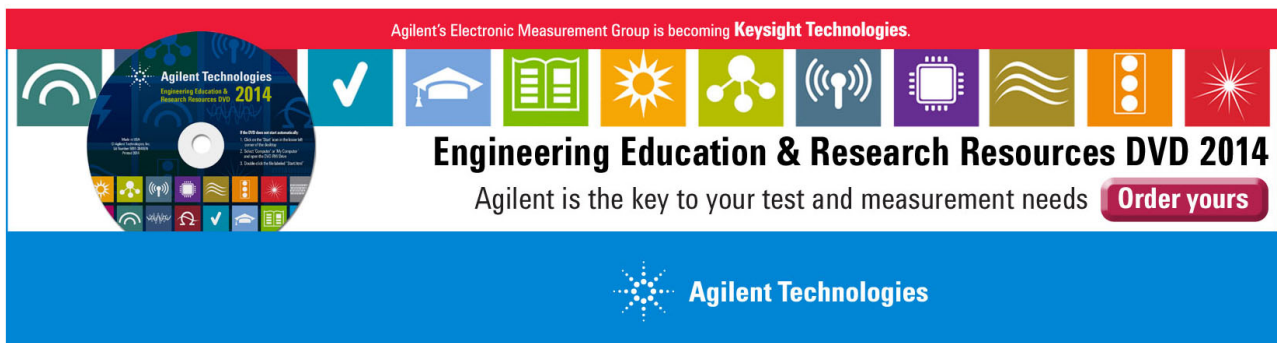The advertisement features a red header with the text 'Agilent's Electronic Measurement Group is becoming Keysight Technologies.' Below this is a row of ten colorful icons representing various engineering and research fields: a Wi-Fi symbol, a checkmark, a graduation cap, an open book, a sun, a network diagram, a radio tower, a microchip, a sine wave, a vertical bar chart, and a starburst. To the left of these icons is a DVD-ROM with the text 'Agilent Technologies Engineering Education & Research Resources DVD 2014'. Below the icons, the text reads 'Engineering Education & Research Resources DVD 2014' in a large, bold font, followed by 'Agilent is the key to your test and measurement needs' and a red button that says 'Order yours'. At the bottom, the Agilent Technologies logo and name are displayed on a blue background.

Tunable fishnet metamaterials infiltrated by liquid crystals

Alexander Minovich,^{a)} Dragomir N. Neshev, David A. Powell, Ilya V. Shadrivov, and Yuri S. Kivshar

Nonlinear Physics Center, Research School of Physics and Engineering, Australian National University, Canberra ACT 0200, Australia

(Received 2 March 2010; accepted 17 April 2010; published online 10 May 2010)

We analyze numerically the optical response and effective macroscopic parameters of fishnet metamaterials infiltrated with a nematic liquid crystal. We show that even a small amount of liquid crystal can provide tuning of the structures due to reorientation of the liquid crystal director. This enables switchable optical metamaterials, where the refractive index can be switched from positive to negative by an external field. This tuning is primarily determined by the shift in the cut-off wavelength of the holes, with only a small influence due to the change in plasmon dispersion.

© 2010 American Institute of Physics. [doi:10.1063/1.3427429]

Metamaterials have attracted a great attention due to their unusual electromagnetic properties not available in nature.¹ One of the important metamaterial designs that is suitable for scaling to optical frequencies is the fishnet metal-dielectric-metal structure.²⁻⁷

Due to the strong local field enhancement within the metamaterials, there emerge new opportunities for external control of their properties or changing their operating bandwidth. There are several means to achieve such tunability, including structural,⁸ temperature,^{9,10} electro-optic,^{11,12} magneto-optic,¹³ and nonlinear tuning.^{14,15} However, so far there are no works on tuning the optical properties of realistic structures with negative index, such as the fishnet structure.

In this paper, we numerically analyze the tunability of optical fishnet metamaterials exhibiting negative refractive index. We study a structure with the holes infiltrated by liquid crystals and demonstrate that even a small amount of liquid crystal can allow for substantial tunability of such structures, including reversal of the sign of the refractive index. This is achieved by employing the reorientation of the liquid crystal director using an external field, as well as by implementing the temperature dependence of the liquid crystal refractive index.

Liquid-crystal tunability of metamaterials has been suggested as a path to achieve tunable negative-index metamaterials.¹⁶ Subsequent studies have explored this idea in quasi-two-dimensional nanostrip geometry,^{17,18} a wire medium,¹⁹ and multilayer omega patterns (for microwave frequencies).²⁰ Recent experiments demonstrated thermal tunability of optical metamaterials, however, the realized structures only experienced a negative magnetic response, and did not show a negative refractive index.⁹ Therefore, here we present a study on tuning of optical fishnet structures as an important step in achieving tunable negative-index optical metamaterials.

Following our recent experiments,⁷ we consider a trilayer metal-dielectric-metal structure patterned with a two-dimensional square lattice of rectangular holes through all three layers. The structure is deposited on a glass substrate, as shown in Fig. 1. In our simulations, we use realistic ma-

terial parameters as gold (Au) and zinc-oxide (ZnO) for the metal and the dielectric layers, respectively. We fix the total thickness of the structure, $h=2h_m+h_d=120$ nm, where h_m is the thickness of the gold and h_d is the thickness of the ZnO layers. We use geometric parameters of the square unit cell of $a=200$ nm, $b=350$ nm, and $c=420$ nm (see Fig. 1).

We employ a finite-difference time-domain numerical method performed with commercial software (RSOFT). For simplicity, in our simulations we assume that the glass substrate and surrounding air are semi-infinite with refractive indices $n_1=1.48$ and $n_3=1$, respectively. The refractive index of ZnO is taken $n_{\text{ZnO}}=1.66$ (Ref. 21) and its weak dispersion in the spectral range of 1–2 μm (maximal deviation from 1.66 is 1.1%) allows for a good approximation by a constant value. For the dielectric permittivity of gold we use six-term Drude–Lorentz expression from the RSOFT material library.²² A detailed description of the implementation of the model in RSOFT is given in Ref. 7. In our simulations, we use a non-uniform spatial grid with size varying from 2 nm near the metal-dielectric interfaces to 20 nm in free space. The time step (in the units of ct) is 8×10^{-4} μm . In order to simulate a periodic structure in the (x, y) plane we use periodic boundary conditions on the planes orthogonal to x and y , and perfectly matched layer boundary conditions on the sides orthogonal to z . The structure is excited from the air by a short pulse with a broad spectrum and plane wave front. Several time monitors are used in the simulation to record the electric field components of the reflected and transmitted waves. The monitors are located 4.4 μm from the structure. We performed a convergence study placing the monitors further from the structure and it has shown that at the distance of

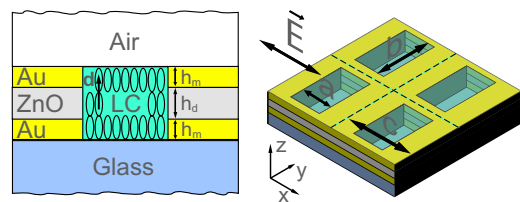


FIG. 1. (Color online) Trilayer fishnet metamaterial on a glass substrate. Left: schematic of the layers. Right: four unit cells of the structure. h_m is the thickness of metal (Au) and h_d is the thickness of dielectric (ZnO). Both substrate and cladding are semi-infinite. Light is polarized along x axis.

^{a)}Electronic mail: min124@gmail.com.

4.4 μm the near field is already negligibly small so only propagating waves are recorded. We take a Fourier transform of the response and normalize it to the incident signal, compensating for the phase shift through air and the substrate. The obtained transmission t and reflection r which are referenced to the surfaces of the metal fishnet.

From the complex coefficients of transmissions and reflection, we can extract the effective refractive index n and the impedance z of the metamaterial structure using the Fresnel formulae.²³ For an equivalent isotropic homogeneous slab of thickness h surrounded by semi-infinite media with refractive indices n_1 and n_3 and normal incidence, the expressions are

$$z = \pm \left[\frac{(1+r)^2 - t^2}{n_1^2(1-r)^2 - n_3^2 t^2} \right]^{1/2}, \quad (1)$$

$$n = \pm \frac{1}{kh} \cos^{-1} \left\{ \frac{1}{t} \frac{n_1(1-r^2) + n_3 t^2}{n_1 + n_3 + r(n_3 - n_1)} \right\} + \frac{2\pi m}{kh}, \quad (2)$$

where m is an integer number. This result agrees with the previously derived formulae in the limit $n_1 = n_3 = 1$, and the same considerations apply to the choice of signs and the branch index m .²⁴ We base our choice of branch on the requirement that n converges in the low frequency limit, and our curves are found to agree with previous results using similar geometrical parameters.^{25,26}

We then apply this extraction approach to determine the change in effective index of the metamaterial when the orientation of the director \mathbf{d} is changed by 90° . We are most interested in the case when such change in the director will switch the refractive index from positive to negative. Therefore, we seek the value of the dielectric layer thickness which maximizes this effect. We perform a number of simulations varying h_d and using two values of the refractive index of the liquid crystal: $n_o = 1.5$ for ordinary waves when the director $\mathbf{d} \parallel \mathbf{y}$ or $\mathbf{d} \parallel \mathbf{z}$ (Fig. 1, left); and $n_e = 1.7$ for extraordinary waves when $\mathbf{d} \parallel \mathbf{x}$. These values correspond to E7 liquid crystal at 25°C .²⁷ We note that in the spectral range of $1-2 \mu\text{m}$ the maximum deviation of the liquid crystal refractive index from these nominal values is 0.25% for n_o and 0.35% for n_e . For simplicity, we also simulate the liquid crystal as a homogeneous medium with isotropic refractive index. This is a reasonable approximation given that the electric field within the holes is mostly oriented in the same direction as the incident field.⁷

The extracted effective refractive index and energy transmission coefficient $T = n_3/n_1 |t|^2$ are presented in Fig. 2 as a function of h_d (varied in 5 nm steps). The negative effective index in the fishnet structures is associated with the excitation of plasmons between the two metal layers,²⁸ and the absorption due to these modes can be seen as transmission dips in Figs. 2(b) and 2(d). The mode excited at longer wavelengths leads to a negative refractive index for a range of thicknesses h_d . There is also a weakly excited mode at shorter wavelengths which can also yield to a negative index if other structural parameters are selected appropriately. Most importantly, we see that the effective refractive index switches from negative to positive value for ZnO thickness of around 25 nm (shown by the dashed line). This effect takes place in a narrow thickness range of only ~ 5 nm, however this is feasible to fabricate with contemporary sputtering techniques that can have a precision of 1 nm.

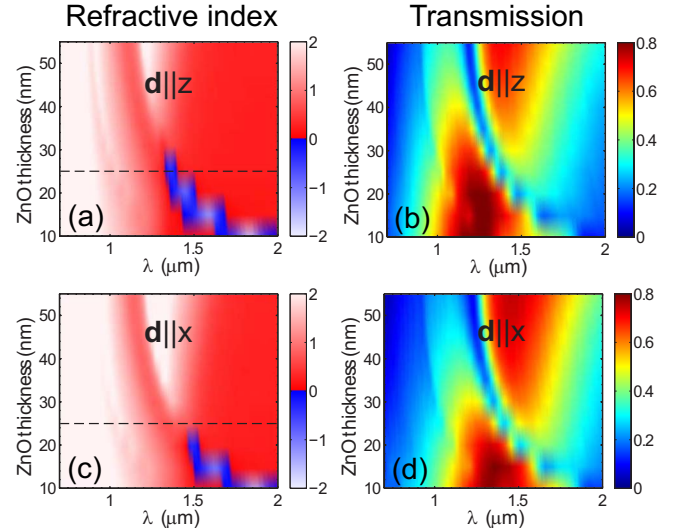


FIG. 2. (Color online) [(a) and (c)] Real part of the effective refractive index of the fishnet structure as a function of ZnO layer thickness. [(b) and (d)] Transmission as a function of ZnO layer thickness. Upper and lower rows correspond to a director of the liquid crystal aligned along z or x axes, respectively.

To understand the effects leading to switching of the effective index for 25 nm ZnO thickness, in Fig. 3 we plot the extracted refractive index, energy transmission, and reflection for both orientations of the liquid crystal director.²⁹ Due to the strong spatial dispersion of the fishnet structure,

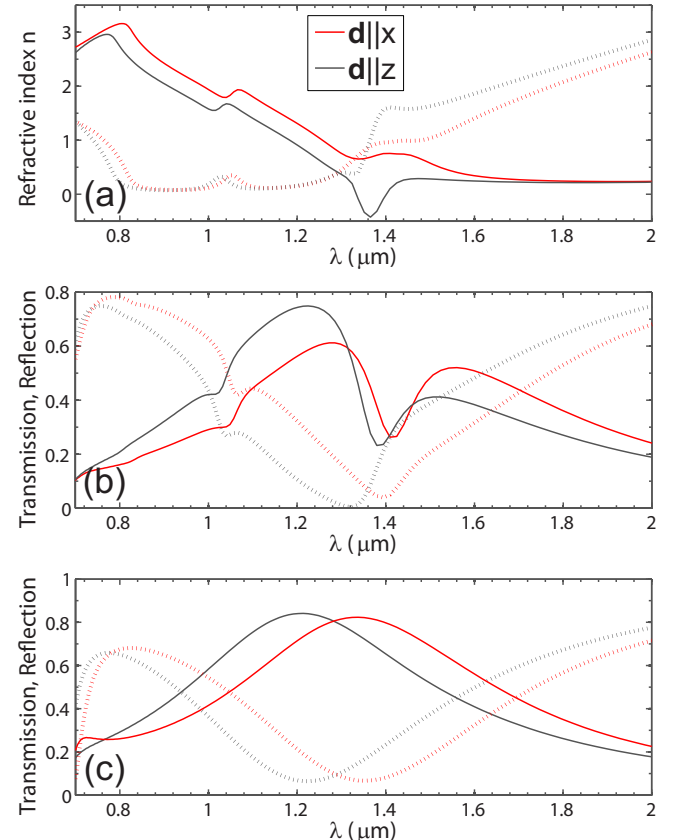


FIG. 3. (Color online) (a) The real (solid line) and imaginary (dotted line) parts of the effective refractive index. (b) Transmission (solid line) and reflection (dotted line). The thickness of ZnO layer $h_d = 25$ nm. (c) Transmission (solid line) and reflection (dotted line) of the respected hole array without ZnO layer. The director orientation is indicated in the legend.

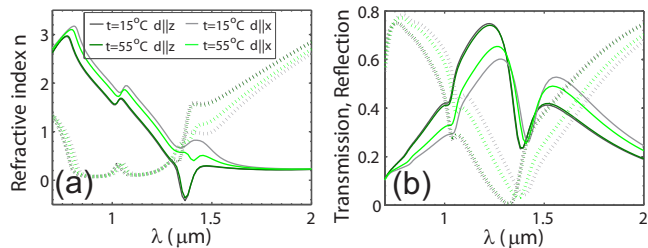


FIG. 4. (Color online) (a) The real (solid line) and imaginary (dotted line) parts of the effective refractive index. (b) Transmission (solid line) and reflection (dotted line). The thickness of ZnO layer is $h_d=25$ nm.

we avoid using the local effective parameters ϵ and μ , since they serve only to reconstruct n and z and lack physical meaning of their own. Instead, we recall that the physical origin of the negative index is a gap plasmonic mode, with a strong magnetic response, lying in the region of plasmlike electrical response of the structure.²⁸ In fact, this effective plasma response exists above a cut-off wavelength that is close to the cut-off wavelength of the fundamental mode of the hole array.

In order to isolate the influence of the hole modes on the response, in Fig. 3(c) we show the calculated transmission through a structure where the ZnO layer is replaced by gold, thus suppressing the gap plasmonic modes. It can be seen that the transmission peak and reflection dip in Fig. 3(b) at around $1.3 \mu\text{m}$ correspond to the cut-off resonance of the hole array, which changes drastically with the change in liquid crystal director orientation. On the other hand, the transmission dip in Fig. 3(b) that corresponds to the plasmonic dispersion curve visible in Fig. 2, barely shifts, since these modes are expected to be largely confined between the metal layers. Thus, when n_{LC} increases, the cut-off wavelength shifts further to the infrared by approximately 170 nm and the hybridization between the hole and plasmon modes which led to the negative index is disturbed.

We also study the effect of temperature on the infiltrated metamaterials due to the strong temperature sensitivity of liquid crystal refractive index, especially near the clearing temperature (58°C for E7). This temperature dependence could potentially disturb the reorientation based tuning of the metamaterials. In Fig. 4 we display the extracted effective refractive index, energy transmission, and reflection at 15°C ($n_o=1.5$, $n_e=1.71$) and at 55°C ($n_o=1.52$, $n_e=1.65$) (Ref. 27) for both orientations of the liquid crystal director. It can be clearly seen that the negative index region undergoes almost no shift with temperature, and that at both temperatures we are able to switch the index between positive and negative, thus the reorientational tuning is robust to temperature.

In conclusion, we have demonstrated numerically the tunability of optical fishnet metamaterials infiltrated by nematic liquid crystals. We have found that by tuning of the director orientation of an anisotropic liquid crystal we can reverse the sign of the effective refractive index of the fishnet metamaterials. We have shown that this tuning is dominated

by a shift in the cut-off frequency of the hole modes, and that the negative index is robust to temperature variations. We believe that our results will facilitate further experimental studies of tunable optical metamaterials.

This work has been supported by the Australian Research Council and from the National Computing Infrastructure Merit Allocation Scheme.

- ¹V. M. Shalaev, *Nat. Photonics* **1**, 41 (2007).
- ²S. Zhang, W. Fan, N. C. Panoiu, K. J. Malloy, R. M. Osgood, and S. R. J. Brueck, *Phys. Rev. Lett.* **95**, 137404 (2005).
- ³G. Dolling, M. Wegener, A. Schaedle, S. Burger, and S. Linden, *Appl. Phys. Lett.* **89**, 231118 (2006).
- ⁴U. K. Chettiar, A. V. Kildishev, H.-K. Yuan, W. Cai, S. Xiao, V. P. Drachev, and V. M. Shalaev, *Opt. Lett.* **32**, 1671 (2007).
- ⁵T. Li, J.-Q. Li, F.-M. Wang, Q.-J. Wang, H. Liu, S.-N. Zhu, and Y.-Y. Zhu, *Appl. Phys. Lett.* **90**, 251112 (2007).
- ⁶J. Valentine, S. Zhang, T. Zentgraf, E. Ulin-Avila, D. A. Genov, G. Bartal, and X. Zhang, *Nature (London)* **455**, 376 (2008).
- ⁷A. Minovich, D. N. Neshev, D. A. Powell, I. V. Shadrivov, M. Lapine, H. T. Hattori, H. H. Tan, C. Jagadish, and Y. S. Kivshar, *Phys. Rev. B* **81**, 115109 (2010).
- ⁸M. Lapine, D. Powell, M. Gorkunov, I. V. Shadrivov, R. Marques, and Y. S. Kivshar, *Appl. Phys. Lett.* **95**, 084105 (2009).
- ⁹S. Xiao, U. K. Chettiar, A. V. Kildishev, V. Drachev, I. C. Khoo, and V. M. Shalaev, *Appl. Phys. Lett.* **95**, 033115 (2009).
- ¹⁰M. J. Dicken, K. Aydin, I. M. Pryce, L. A. Sweatlock, E. M. Boyd, S. Walavalkar, J. Ma, and H. A. Atwater, *Opt. Express* **17**, 18330 (2009).
- ¹¹Q. Zhao, L. Kang, B. Du, B. Li, J. Zhou, H. Tang, X. Liang, and B. Zhang, *Appl. Phys. Lett.* **90**, 011112 (2007).
- ¹²Z. L. Samson, K. F. MacDonald, F. De Angelis, B. Gholipour, K. Knight, C. C. Huang, E. Di Fabrizio, D. W. Hewak, and N. I. Zheludev, *Appl. Phys. Lett.* **96**, 143105 (2010).
- ¹³F. Zhang, Q. Zhao, L. Kang, D. P. Gaillot, X. Zhao, J. Zhou, and D. Lippens, *Appl. Phys. Lett.* **92**, 193104 (2008).
- ¹⁴D. A. Powell, I. V. Shadrivov, Y. S. Kivshar, and M. V. Gorkunov, *Appl. Phys. Lett.* **91**, 144107 (2007).
- ¹⁵I. V. Shadrivov, A. B. Kozyrev, D. W. van der Weide, and Y. S. Kivshar, *Appl. Phys. Lett.* **93**, 161903 (2008).
- ¹⁶I. C. Khoo, D. H. Werner, X. Liang, A. Diaz, and B. Weiner, *Opt. Lett.* **31**, 2592 (2006).
- ¹⁷X. Wang, D.-H. Kwon, D. H. Werner, I. C. Khoo, A. V. Kildishev, and V. M. Shalaev, *Appl. Phys. Lett.* **91**, 143122 (2007).
- ¹⁸D. H. Werner, D.-H. Kwon, I. C. Khoo, A. V. Kildishev, and V. M. Shalaev, *Opt. Express* **15**, 3342 (2007).
- ¹⁹M. V. Gorkunov and M. A. Osipov, *J. Appl. Phys.* **103**, 036101 (2008).
- ²⁰F. Zhang, L. Kang, Q. Zhao, J. Zhou, X. Zhao, and D. Lippens, *Opt. Express* **17**, 4360 (2009).
- ²¹J. M. Khoshman and M. E. Kordesch, *Thin Solid Films* **515**, 7393 (2007).
- ²²A. D. Rakic, A. B. Djuricic, J. M. Elazar, and M. L. Majewski, *Appl. Opt.* **37**, 5271 (1998).
- ²³M. Born, E. Wolf, and A. B. Bhatia, *Principles of Optics* (Cambridge University Press, Cambridge, 1997), pp. 61–70.
- ²⁴D. R. Smith, S. Schultz, P. Markos, and C. M. Soukoulis, *Phys. Rev. B* **65**, 195104 (2002).
- ²⁵G. Dolling, M. Wegener, C. M. Soukoulis, and S. Linden, *Opt. Express* **15**, 11536 (2007).
- ²⁶G. Dolling, C. Enkrich, M. Wegener, C. M. Soukoulis, and S. Linden, *Opt. Lett.* **31**, 1800 (2006).
- ²⁷J. Li, S.-T. Wua, S. Brugioni, R. Meucci, and S. Faetti, *J. Appl. Phys.* **97**, 073501 (2005).
- ²⁸A. Mary, S. G. Rodrigo, F. J. Garcia-Vidal, and L. Martin-Moreno, *Phys. Rev. Lett.* **101**, 103902 (2008).
- ²⁹C. Menzel, T. Paul, C. Rockstuhl, T. Pertsch, S. Tretyakov, and F. Lederer, *Phys. Rev. B* **81**, 035320 (2010).